

Strength properties of cement mortar when Cement partially replaced with Silica fume and GGBS

Etaveni.Madhavi¹, Praveen Mailaram², Nalla Sharath Kumar³,
Kadapa Vinod Kumar⁴, Korra Ram Babu⁵ &
Bomma Praveen Kumar⁶

¹ Research Scholar, KLU and Assistant Professor, Civil Engineering, Sri indu Engineering College,
Telagana, India.

^{2,3,4,5,6} UG students, Sri indu Engineerin College, Telagana, India.

Abstract: Concrete is one of the important construction material used in the world of all engineering works, including the infrastructure development proved that, it is a cheap material and its constituents are widely available in nature. Due to widespread usage and fast infrastructure development in all over the world, there is a shortage of natural aggregates, Such as fine aggregate and coarse aggregate. These materials are available with high cost, to prevent this the fine aggregate and coarse aggregate can be replaced with waste materials. In this project cement mortar is partially replaced by silica fume and ggbs accordingly in the range of 0%, 10%, 20%, & 30% by 1:3 cement mortar. Specific gravity is done for silica fume and ggbs. Cement mortars are casted, tested and compared with conventional mortar.

These tests were carried out to evaluate the strength properties for 7, and 28 days.

Key Words: GGBS 1, silica fume2, Compressive Strength

1.INTRODUCTION 1

For Past many years construction industry has been making some progress in the utilization of waste materials in concrete. Some of waste products are fly ash, rice husk, saw dust, discarded tires, e-waste, glass, bagasse ash, stone dust, silica fume and ceramic. Proper use of waste products provides viable economy and healthy environment. Each waste product has its specific effect on the properties of fresh and hard concrete. There has been a long-term growing demand for aggregates to produce concrete and this has presented increased problems of supplying of sand and gravel .Previous

researches have shown crushed stone dust can be used to replace the natural sand in concrete .Recycle aggregates are also being studied though some loss in workability and mechanical property is reported .The ceramic industry has about 30% to 50% failed products due to improper mixing or heating conditions so ceramic can be used as a coarse aggregates Present study has been done to evaluate the suitability of such waste materials in concrete production.

2. MATERIALS USED 2

2.1 Cement 1

In this experiment 43 grade ordinary Portland cement is used. The testing of cement is done as per IS Code the specific gravity of cement found is 3.10.

2.2 Fine Aggregates 2

In this experiment the locally available sand is used and the specific gravity of fine aggregate is done by using the IS 2720 part 3 code. The specific gravity is found 2.62. The fine aggregates used which passes through the 4.75mm sieve.

2.3 Properties of Silica fume 3

Silica fume also known as micro silica is an amorphous (non-crystalline) polymorph of silicon dioxide, silica. It is an ultrafine powder collected as a byproduct of silicon and production and Ferro -silicon alloy consists of spherical particles with an average particle diameter of 150nm.

Chemical properties of silica fume:

Chemical	Percentage
SiO ₂	85
Al ₂ O ₃	1.12
Fe ₂ O ₃	1.16
CaO	0.2-0.8
MgO	0.2-0.8
Na ₂ O	0.5-1.2
K ₂ O	0.5-1.2

2.4 Water

The least expensive but the most important ingredient of concrete is water. The water which is used for mixing concrete should be clean and free from harmful impurities such as oil, alkali, acid etc. portable water was used for mixing and curing work.

2.6 Properties of GGBS

Ground granulated blast furnace slag is obtained by the quenching molten iron slag from a blast furnace in water, to produce a glassy, granular product that is then dried and ground in to a fine powder. Table 1 will show the properties of GGBFS.

Chemical properties of GGBS

Chemical	Percentage
CaO	30-50
SiO ₂	28-38
Al ₂ O ₃	8-24
MgO	1-18

3. TESTS 3

3.1 Compressive strength 1

The test is done for 28days and the size of the cube 70.6mmx70.6mmx70.6mm. The concrete mix design is carried out for (1:3) mix grade. The cubes are tested on 2000KN capacity universal testing machine. Compression test has been conducted confirming to IS 516-1959(5), on the concrete specimens in the universal testing 200MT. in this text cube is placed with the cast faces not in contact with the platens of testing machine. Load has been applied at a constant rate of stress equal to 15mpa/min according to the relevant IS code and the load at which the specimens failed has been recorded. Thus from the results, the compressive strength is obtained.

4. RESULTS 4

4.1 Compression Test 1


In this study the cubes are prepared with silica fume and ggbs. Totally 36 cubes are casted and tested for 7days and 28days. Mortars are casted for

two different proportions and for 2 different age periods for every age period 3 cubes are casted. The size of cube is 70.6mmX70.6mmX70.6mm. The most and useful parameters is compressive strength because it is a desirable characteristic of cement mortar properties and also quantitatively related to compressive strength.


The replacement of cement with silica fume 5% and GGBS 30% strength is increased when compared to normal mortar

The replacement of cement with silica fume 10% and GGBS 30% strength is increased when compared to normal mortar.

The compressive strengths are shown in bar charts

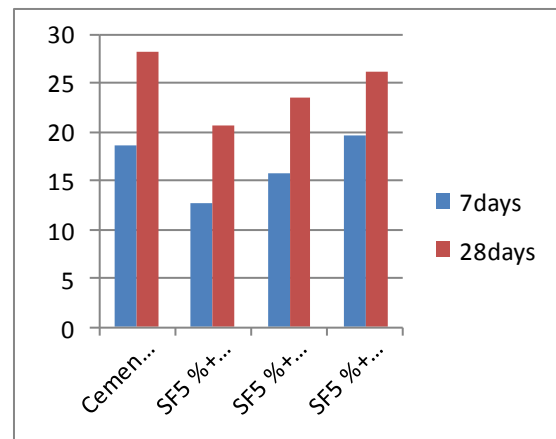

Influence of Silica fume 5% and GGBS 10%, 20%, 30% Development of Compressive Strength of Cement Mortar (1:3)

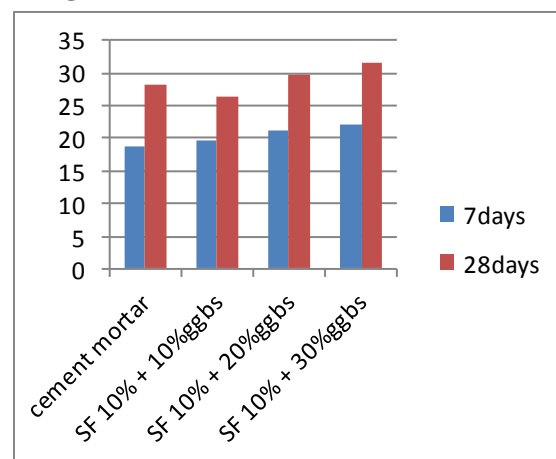

Influence of Silica fume 5% and GGBS 10%, 20%, 30% Development of Compressive Strength of Cement Mortar (1:3)

5. CONCLUSIONS 5

A. *Based on the present experimental investigation the following conclusion are drawn*

- At the Replacement of 10%, 20% GGBS and 5% silica fume with cement got less strength when compared to cement mortar.
- At the Replacement of 10%, 20% GGBS and 10% silica fume with cement got less strength when compared to cement mortar.
- At the Replacement of 30% GGBS and 10% , 5% silica fume with cement got more strength when compared to cement mortar.
- It can be conclude that silca fume can not be replaced alone, when ggbs 30% and silica fume 5% or 10% can be replaced to get more strength.

REFERENCES

1. **R M Senthamarai & P. Devadas Manoharan.** Have studied use of hazardous industrial waste in concrete making will lead to greener environment.
2. **C. Medina a, M.I. Sanchez de, Rojas b, M. Fries b.** Have studied to investigated the reuse of ceramic waste as coarse aggregate in co-efficient concretes.
3. **Yingzi Yang, Michael D. Lepech, En-Hua Yang, Victor C. Li,** '*Self-healing of Engineered Cementitious Composites (ECC)*' Department of Civil and Environmental Engineering University of Michigan, Ann Arbor, MI 48109-2125, USA, 2009. (10)
4. **HanifBinici.** Have studied the Durability of concrete made with granite and marble as recycle aggregates.
5. S.Arivalagan : "Sustainable Studies on concrete with GGBS as a replacement of cement" Jordal Journal of civil engineering, vol 8 no3, 2014.